

Comparitive Evaluation of Novel Desensitising Agents on Dentinal Tubule Occlusion-A Scanning Electron Microscopic Study

Dr. Madhavi Ajit Shetty¹, Dr. Sharad Kokate² and Dr. Vibha Hegde³

¹ YMT Dental College and Hospital

Received: 9 December 2019 Accepted: 4 January 2020 Published: 15 January 2020

Abstract

Aim: To comparatively evaluate the occlusion of dentinal tubules by four novel desensitizing agents for treatment of Dentinal Hypersensitivity. **Materials and Methods:** The Diode Laser and three commercially available Desensitizers the NovaminR group- (SHY-NMTM), Colgate Sensitive Pro-relief, Gluma were investigated in this study. 30 extracted mandibular molars were used (n=30). They were divided into 5 groups including the control group in which no treatment was done. Teeth were ground under water-cooled trimming wheel, to prepare flat dentin surfaces. The dentin surfaces were etched to remove any smear plugs and to mimic the open dentinal tubules of sensitive dentin using 0.5 M Ethylene Diamine Tetraacetic Acid (pH 7.4) for two minutes (applied with a micro brush) and then rinsed with an air-water syringe for 30 seconds. **Materials and Methods:** The Diode Laser and three commercially available Desensitizers the Novamin R group- (SHY-NM TM), Colgate Sensitive Pro-relief, Gluma were investigated in this study. 30 extracted mandibular molars were used (n=30). They were divided into 5 groups including the control group in which no treatment was done. Teeth were ground under watercooled trimming wheel, to prepare flat dentin surfaces. The dentin surfaces were etched to remove any smear plugs and to mimic the open dentinal tubules of sensitive dentin using 0.5 M Ethylene Diamine Tetraacetic Acid (pH 7.4) for two minutes (applied with a micro brush) and then rinsed with an air-water syringe for 30 seconds.

Index terms— dentinal hypersensitivity; novamin; gluma; diode laser, pro-arginine; scanning electron microscope.

1 Introduction

entinal Hypersensitivity (DH) is defined as one of the most painful and least predictably treated chronic conditions in dentistry. 1 The nature of the exposed dentin is of relevance, as not all patients exhibiting dentin exposure will develop sensitivity. The number and diameter of dentinal tubules at the tooth surface is shown to be significantly increased in hypersensitive dentin. 2,3 While the exact mechanism of dentinal hypersensitivity is still controversial, hydrodynamic theory is one of the most accepted hypothesis. 4 The dentinal tubules, which are open and wide, contain a fluid. According to this theory, this fluid expands when exposed to heat and contracts when exposed to cold or touch. The contraction and expansion change the pressure in the fluid phase, which in turn activates mechanoreceptor nerves close to the pulp. When nerve receptors are activated, sodium ions enter the dentin and potassium exits. This ion exchange polarizes the nerves and causes pain. 3 The concept of tubule occlusion as a method of dentin desensitization is a logical conclusion based on the hydrodynamic hypothesis. 5 The two principal treatment options available are, preventing fluid flow, plugging the dentinal tubules, or desensitizing the nerve, making it less responsive to stimulation. 6 In the last fifteen years, with the

introduction of Lasers which gave further possibilities to DH therapy. 7,[8][9][10][11] It is now possible to show that the role of laser in DH therapy is twofold. The low-level power lasers also called "soft lasers," act directly on nerve transmission. The other, high-power lasers such as diode 980 nm and 808 nm, Nd: YAG 1064 nm, CO₂ 10600 nm, Er, Cr: YSGG 2780 nm, and Er: YAG 2940 nm act on DH by provoking a melting effect along with the crystallization of dentine inorganic component and also the coagulation of fluids into the dentinal tubules. 12 Among the "high power" devices, the diode lasers which are the most studied and also the ones that gave the best results in several clinical protocols even in very highgrade DH cases.

Gluma desensitizer, (Heraeus Kulzer GmbH, Wehrheim, Germany), is a combination product consisting of an aqueous solution of 35% hydroxyethyl methacrylate and 5% glutaraldehyde, that has been reported to have been an effective desensitizing agent. The glutaraldehyde intrinsically blocks dentinal tubules, counteracting the hydrodynamic mechanism that leads to dentin hypersensitivity. 13 A new product consisting of calcium sodium phosphosilicate NovaMin R, (SHY-NM TM), has now been introduced. NovaMin is the trade name that has been given to bioactive glass (e.g., Bioglass), that has been ground into a fine particulate with a median size of less than 20 microns. It reduces sensitivity by blocking open tubules and by supplying calcium (Ca²⁺) and phosphate (PO₄³⁻) ions to form hydroxycarbonate apatite (HCA). It is composed of elements that are naturally occurring in the body and it reacts to form a mineral layer that is chemically and structurally very similar to natural tooth material. 14 In 2009, Colgate-Palmolive company acquired the rights to the novel technology, now known as Pro-Argin technology, first introduced by Kleinberg et al in 2002, The pro-arginine therapy uses arginine, an amino acid, calcium carbonate a source of calcium and Bicarbonate pH buffer. 15 The main objective of this study was to evaluate and compare the occlusion of dentinal tubules for treatment of DH by four novel Desensitizing agents:

In-Office Treatment: Diode Laser (Zolar) and Gluma Desensitizer.

Patient Applied Products for Home Use: Novamin R containing Toothpaste (SHY-NM TM) and Colgate Sensitive Pro-Relief Toothpaste.

2 II.

Materials and Methods a) Sample preparation: Thirty freshly extracted mandibular molars were selected and stored in normal saline until use(n=30)

The teeth were cleaned of any gross debris. Tooth cuts were made with a carborundum disc attached to a cutting machine. The crown and the apical third of each tooth were removed, and the remaining teeth were sectioned to provide one to two dentin specimens each. Sectioned samples of 2-mm thickness were made. The dentin specimens were then placed for 30 seconds in an ultrasonic cleaner in distilled water, etched with 17% aq EDTA (Ethylene Diamine Tetra Acetic Acid) for 2 minutes to remove the smear layer and rinsed in distilled water. The control specimens were then dried, and the test specimens were treated as per the manufacturer's instructions with the desensitizing agents.

b) Desensitising Agents: 30 extracted mandibular molars were used. (n=30) They were divided into 5 groups including the control group in which no treatment was done. The Diode Laser and three commercially available desensitizers were investigated in this study.

Group 1: Diode laser (ZOLAR) at 980nm therapy was used on dentin discs, in a non-contact mode for 30 seconds.

Group 2: Novamin R containing toothpaste SHY-NM TM Is applied on the dentin discs for 30-40 seconds using an applicator tip and air-dried. Group 3: Gluma desensitizer (Heraeus Kulzer GmbH, Wehrheim, Germany) is applied on the dentin discs for 30-40 seconds using applicator tip and air-dried Group 4: Pro-arginine group of toothpaste Colgate sensitive pro-relief is applied on the dentin discs and left for 30-40 seconds using applicator tip and air-dried. III.

3 Results

The total number of tubules was counted from the various images captured by the SEM. Out of the total tubules, those that were completely occluded, partially occluded, and open tubules were counted. The ratio of completely occluded tubules to the total tubules as well as the ratio of partially occluded tubules to the total tubules were calculated. Nonparametric tests were done as the data obtained did not show a normal distribution. The data obtained was statistically analyzed using the Kruskal-Wallis test and Wilcoxon rank-sum test, through which comparison among the groups as well as an intergroup comparison was performed, respectively, and statistical significance was calculated (Table 1). The mean of the ratio of completely occluded tubules to total tubules and partially occluded to total tubules for each group were plotted (Figs. 2 and 3). All of the statistical analyses were performed using IBM SPSS ver. 21 (IBM Co., Armonk, NY, USA).

After combining the mean values of occluded tubules/total number (partial and total) the more occluded tubules were seen in this order Group 1>Group 2>Group 3> Group 4 IV.

4 Discussion

Dentin Hypersensitivity is defined as a pain arising from exposed dentin, typically in response to chemical, thermal, or osmotic stimuli, that can't be explained as arising from any other form of dental defect or pathology.

16 SEM studies of hypersensitive dentin surfaces reveal that they need more patent tubules per unit area than nonsensitive dentin. Absi et al. 17 19 Dentine tubule occlusion is achieved in two different ways, either by the deposition of an occluding layer on top of the dentin or by the introduction of occluding material into dentine tubules.

In the Morris et al. 20 study they highlighted a very powerful placebo effect inherent in clinical dentin sensitivity studies, particularly when dealing with small numbers of subjects and eligible teeth. Furthermore, the large standard deviations reported by Morris et al. 20 because of the highly subjective nature of pain and/or the variability of the individual pain response reported in dentin sensitivity studies, makes it extremely difficult to detect significant differences between groups without utilizing a large number of subjects. Thus, the in vitro examination of products using a reproducible model such as the dentin disc, can aid the understanding of the potential occluding, and thus desensitizing properties of possible desensitizing agents. 21 Conventional therapies for the treatment of DH comprehend the topical use of desensitizing agents, either professionally or by using protein precipitants, 22 tubule-occluding agents, 23,24 tubule sealants, 25 and, recently, lasers. 26 Several studies 27-29 describe a synergistic action of lasers using desensitizing agents. The laser system can favor the permanence of the desensitizer for a longer time than when they are used alone. For this reason, if a laser device is employed additionally to a standard desensitizing agent, the latter remains above the tooth surface for 60 seconds before the irradiation.

Focusing on the effectiveness of only the diode laser, this was investigated by several authors. Matsumoto et al. 30 showed an 85% improvement in teeth treated with a laser; Aun et al. 31 reported success in laser-irradiated teeth in 98% of their cases; Yamaguchi et al. 32 noticed an effective improvement index of 60% within the group treated with laser compared to the 22.2% of the control non-lased group; Another study administered by Brugnera et al. showed the immediate analgesic effect using a diode laser. 33 Gluma desensitizer is a solution containing 5% glutaraldehyde and 35% hydroxyethyl methacrylate. Because glutaraldehyde is a biological fixative, it has been suggested that the dentinal tubules are occluded as an effect of reaction with plasma proteins from a dentinal fluid. Hydroxyethyl methacrylate is a hydrophilic monomer compound of dentin bonding agents with the ability to infiltrate into acid-etched and moist dental hard tissue. 34 NovaMin R (SHY-NM TM) is a bioactive glassceramic material that falls into a class of newer materials that provide calcium and phosphate upon reaction. In the case of products with NovaMin, the active ingredient, calcium sodium phosphosilicate that reacts when exposed to aqueous media and provides calcium and phosphate ions that form a HydroxyCarbonate Apatite (HCA) with time. 35 The combination of the residual NovaMin particles and the HCA layer results in the physical occlusion of dentinal tubules, which will relieve hypersensitivity . 36 The results of the present study revealed that NovaMin-treated dentin specimens showed more complete tubule occlusion. This is in accordance with the findings of Litkowski 14 and Du Min et al. 37 who found NovaMin to be a more effective desensitizer.

Pro-arginine, the effective components of this new technology are Arginine, an amino acid positively charged at physiologic pH (6.5-7.5), Bicarbonate, a pH buffer, and insoluble Calcium carbonate, a source of calcium. The arginine present in the products is obtained from vegetable sources. In 2009, Colgate-Palmolive launched Colgate Sensitive Pro-Relief in-office desensitizing paste. 39 When the desensitizing paste is applied to exposed dentin, Arginine (positively charged) and calcium carbonate, found in saliva naturally, work together to accelerate the natural mechanisms of occlusion by binding to the negatively charged dentine surface to deposit a dentin-like mineral, as a plug within the dentin tubules and a protective layer on the dentin surface. This consists of arginine, calcium carbonate, phosphate, and salivary glycoproteins. Freeze fracture images have shown that this plug reaches a depth of 2 µm into the tubule. It is effective in reducing dentin fluid flow thereby relieving hypersensitivity. 39 In the present study, we have shown that professionally applied dental (in-office) products containing Diode Laser (Zolar) and Gluma desensitizer are both capable of occluding the dentin tubules to varying degrees and may have the clinical potential to reduce dentin hypersensitivity.

5 Year

6 Global

In house application of dental products like Colgate Sensitive Pro-relief and Novamin (SHY-NM), also occluded dentinal tubules and reduced dentin hypersensitivity.

All the novel desensitizers occluded the tubules but Diode laser and NovaMin have shown superior results with respect to complete tubule occlusion on initial application. The results of the present study are limited to physical findings of the change in the dentinal tubules and do not present in vivo differences that may result from the physiological effect of these desensitizing agents. Differences between our results and those of other studies may be related to the dentin specimen utilized, etching process, time and mode of application of the desensitizing agent, or a combination of these variables. Further future clinical trials with larger sample size, comparison with positive controls and negative controls, different concentration should be taken under consideration to validate the result of this new product as an efficacious desensitizing agent. However, the results were consistent in demonstrating a significant effect in reducing the sensitivity with the desensitizing agents used.

V.

7 Conclusion

In conclusion, NovaMin R (SHY NM TM) and laser diode therapy showed a greater number of completely occluded tubules and Gluma desensitizer and Colgate sensitive Pro-relief produced a greater number of partially occluded tubules.

There was a statistically significant difference between the five groups when the ratio of complete and partial occlusion was calculated against the total number of tubules.

Hence, the Diode Laser application and NovaMin R (SHY NM TM) application could be more effective in providing relief from dentinal hypersensitivity.

8 Financial support and sponsorship: Nil

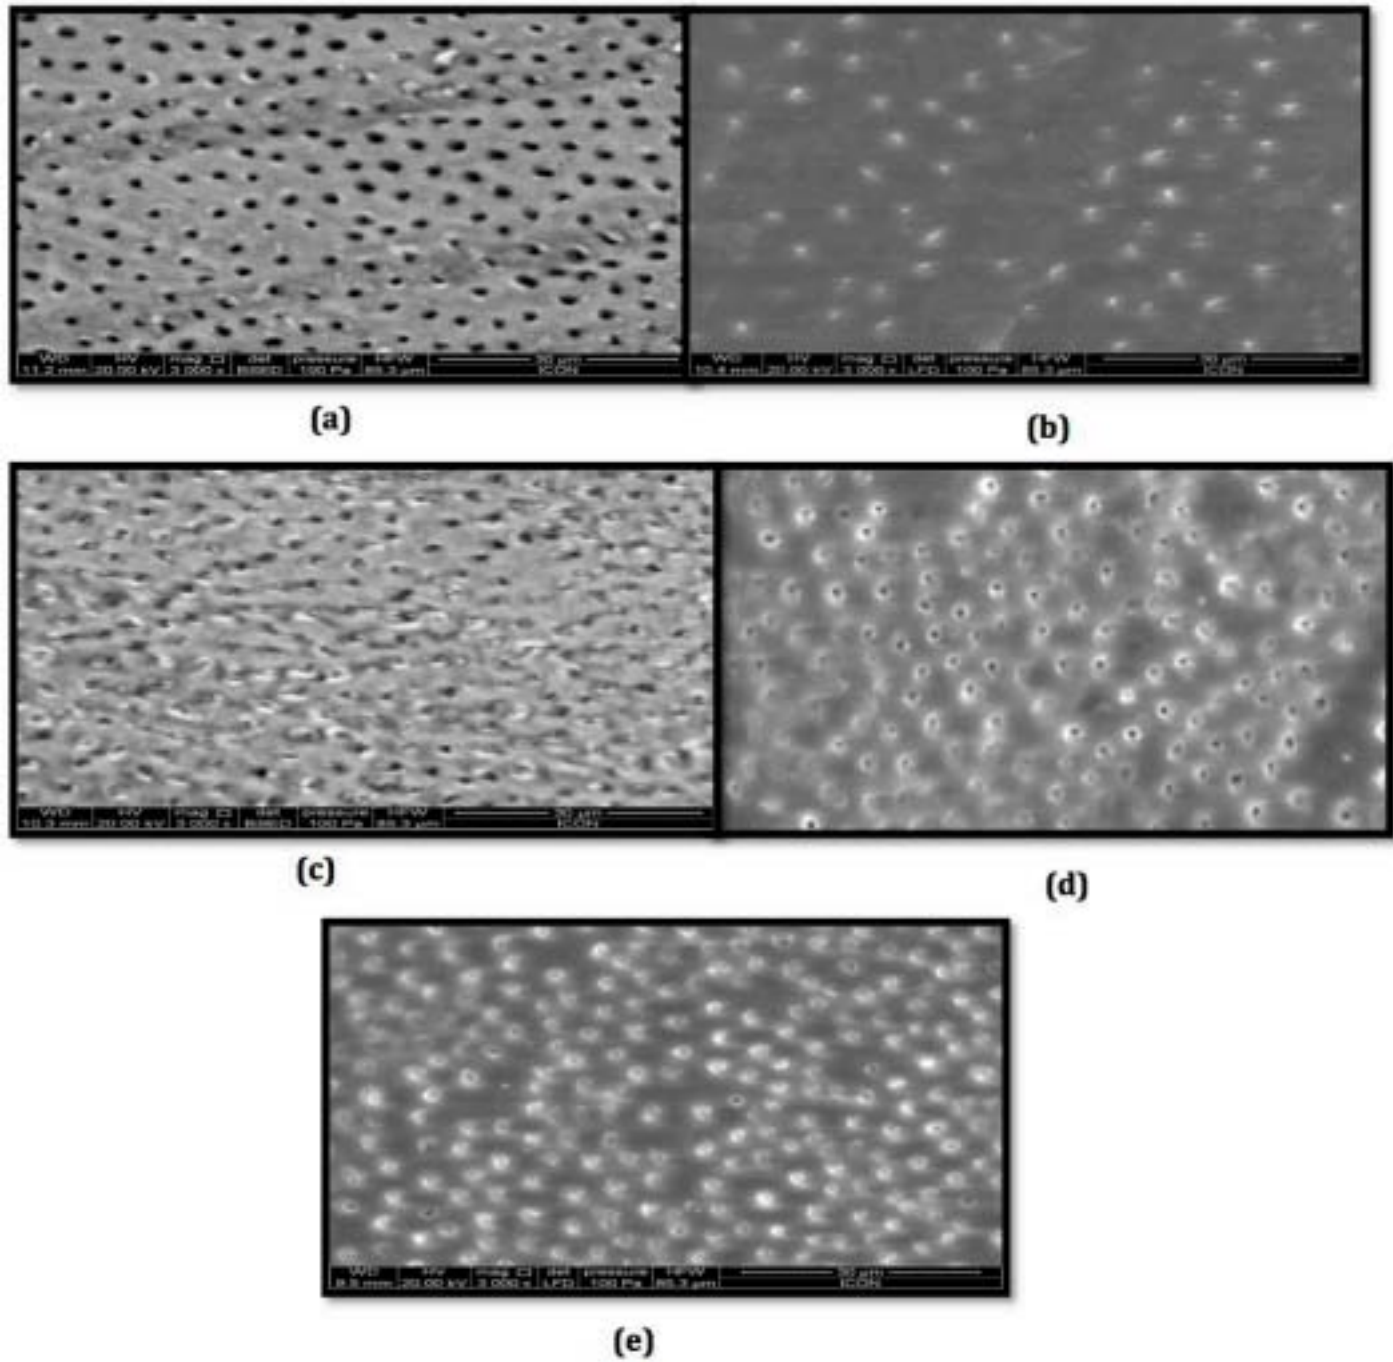


Figure 1:

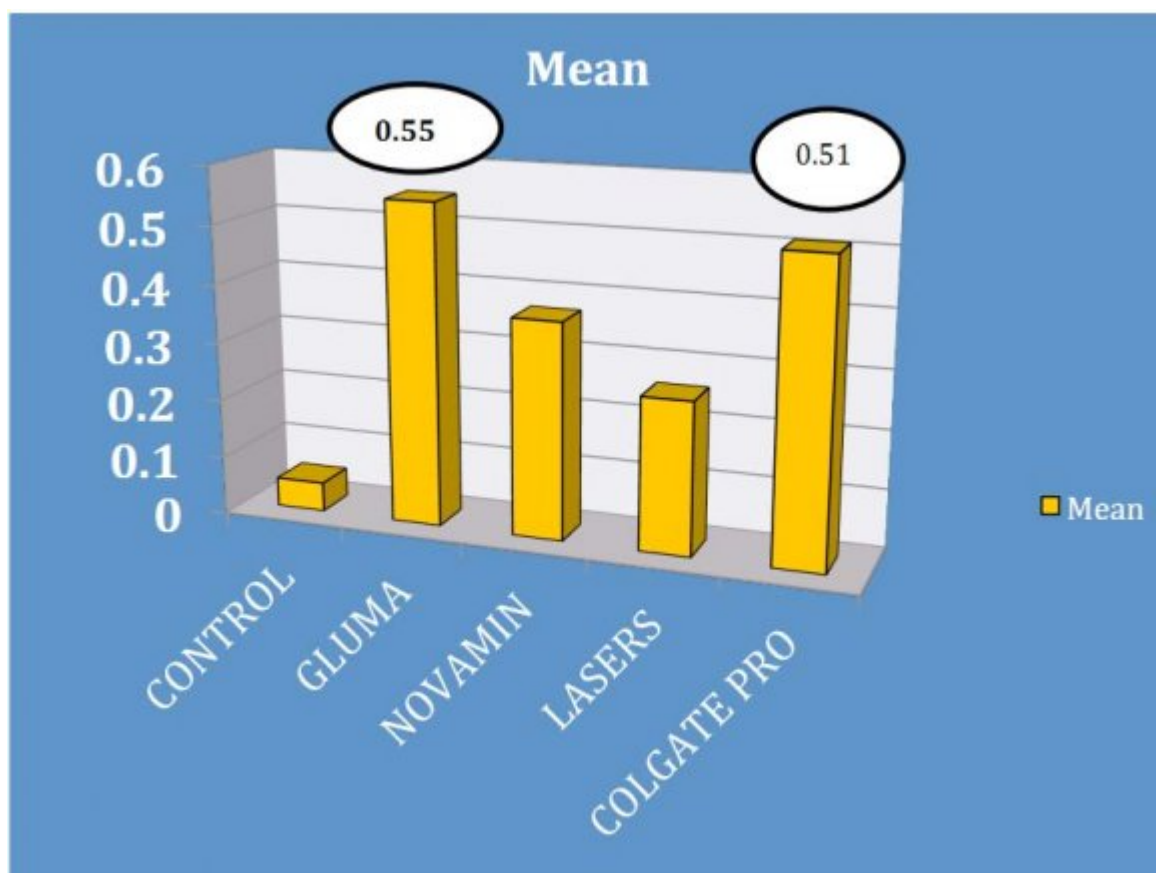


Figure 2:

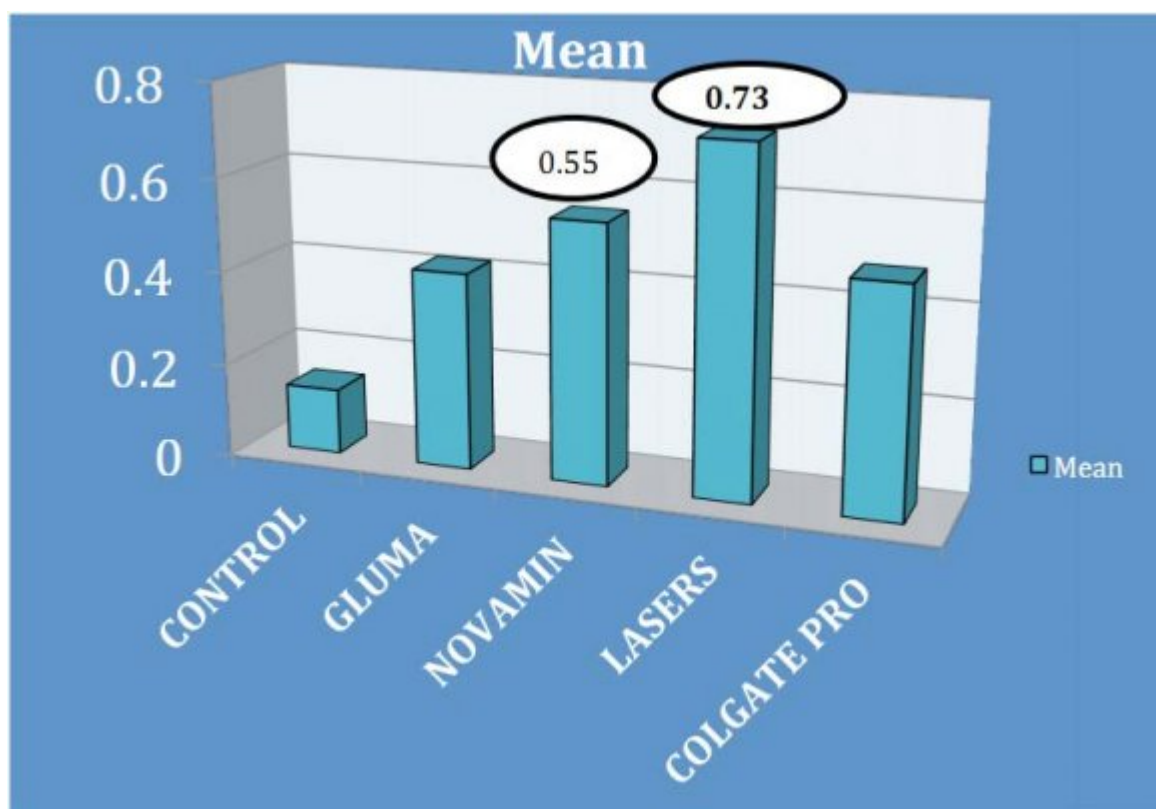


Figure 3: J

		PARTIALLY OCCLUDED		TOTALLY OCCLUDED	
		Mean	SD	Mean	SD
Groups	CONTROL	.05	.01	.14	.01
	GLUMA	.55	.03	.42	.01
	NOVAMIN	.37	.01	.55	.02
	LASERS	.26	.02	.73	.02
	COLGATE PRO SENSITIVE	.51	.01	.48	.01

Figure 4: Figure 1

1

Figure 5: Table 1 :

-
- [Rees and Addy ()] 'A cross-sectional study of dentin hypersensitivity'. J S Rees , M Addy . *Journal of Clinical Periodontology* 2002. 29 (11) p. .
- [Jacobsen and Bruce ()] 'Clinical dentin hypersensitivity: understanding the causes and prescribing a treatment'. P L Jacobsen , G Bruce . *J Contemp Dent Pract* 2001. 2 p. .
- [Morris et al. ()] 'Clinical efficacy of two dentin desensitizing agents'. M F Morris , R D Davis , B W Richardson . *Am J Dent* 1999. 12 p. .
- [Du Min et al. ()] 'Clinical evaluation of a dentifrice containing calcium sodium phosphosilicate (novamin) for the treatment of dentin hypersensitivity'. Q Du Min , Z Bian , H Jiang , D C Greenspan , A K Burwell , J Zhong . *Am J Dent* 2008. 21 p. .
- [Yamaguchi et al. ()] 'Clinical study on the treatment of hypersensitive dentin by GaAlAs laser diode using the double-blind test'. M Yamaguchi , M Ito , T Miwata . *Aichi Gakuin Daigaku Shigakkai shi* 1990. 28 (2) p. .
- [Gangarosa ()] 'Current strategies for dentistapplied treatment in the management of hypersensitive dentine'. L P Gangarosa . *Archives of Oral Biology* 1994. 39 (1) p. .
- [Wichgers and Emert ()] 'Dentin hypersensitivity'. T G Wichgers , R L Emert . *General Dentistry* 1996. 44 (3) p. .
- [Absi et al. ()] 'Dentin hypersensitivity. A study of the patency of dentinal tubules in sensitive and non-sensitive cervical dentin'. E G Absi , M Addy , D Adams . *Journal of Clinical Periodontology* 1987. 14 (5) p. .
- [Pesevska et al. ()] 'Dentinal hypersensitivity following scaling and root planing: comparison of low-level laser and topical fluoride treatment'. S Pesevska , M Nakova , K Ivanovski . *Lasers in Medical Science* 2010. 25 (5) p. .
- [Kerns et al. ()] 'Dentinal tubule occlusion and root hypersensitivity'. D G Kerns , M J Scheidt , D H Pashley , J A Horner , S L Strong , T E Van Dyke . *Journal of Periodontology* 1991. 62 (7) p. .
- [Absi et al. ()] 'Dentine hypersensitivity: a study of the patency of dentinal tubules in sensitive and non-sensitive cervical dentine'. E G Absi , M Addy , D Adams . *J Clin Periodontol* 1987. 14 p. .
- [Schwarz et al. ()] 'Desensitizing effects of an Er: YAG laser on hypersensitive dentine: a controlled, prospective clinical study'. F Schwarz , N Arweiler , T Georg , E Reich . *Journal of Clinical Periodontology* 2002. 29 (3) p. .
- [Zhang et al. ()] 'Effects of CO2 laser in the treatment of cervical dentinal hypersensitivity'. C Zhang , K Matsumoto , Y Kimura , T Harashima , F H Takeda , H Zhou . *Journal of Endodontics* 1998. 24 (9) p. .
- [Arrais et al. ()] 'Effects of desensitizing agents on dentinal tubule occlusion'. C A Arrais , D C Chan , M Giannini . *J Appl Oral Sci* 2004. 12 p. .
- [De Assis Cde et al. ()] 'Efficacy of Gluma Desensitizer on dentin hypersensitivity in periodontally treated patients'. A De Assis Cde , R P Antoniazzi , F B Zanatta , C K Rosing . *Braz Oral Res* 2006. 20 p. .
- [Rajesh et al. ()] 'Evaluation of the efficacy of a 5% calcium sodium phosphosilicate (Novamin) containing dentifrice for the relief of dentinal hypersensitivity: a clinical study'. K S Rajesh , S Hedge , Arun Kumar , M S Shetty , DG . *Indian J Dent Res* 2012. 23 p. .
- [Sicilia et al. ()] 'Immediate efficacy of diode laser application in the treatment of dentine hypersensitivity in periodontal maintenance patients: a randomized clinical trial'. A Sicilia , S Cuesta-Frechoso , A Suárez , J Angulo , A Pordomingo , De Juan , P . *Journal of Clinical Periodontology* 2009. 36 p. .
- [Watanabe et al. ()] 'In vitro and in vivo studies on the application of erbium: YAG laser for dentine hypersensitivity'. H Watanabe , K Kataoka , H Iwami , T Shinoki , Y Okagami , I Ishikawa . *International Congress Series* 2003. 1248 p. .
- [Brugnera et al. (2001)] 'LLLT in treating dentinal hypersensitivity: a histologic study and clinical application'. A Brugnera , F Zanin , A Pinheiro . *Proceedings of the 2nd International Conference on Near-Field Optical Analysis: Photodynamic Therapy & Photobiology Effects (NOA '02)*, (the 2nd International Conference on Near-Field Optical Analysis: Photodynamic Therapy & Photobiology Effects (NOA '02)Houston, Tex, USA) June 2001. p. .
- [Moritz et al. ()] 'Longterm effects of CO2 laser irradiation on the treatment of hypersensitive dental necks: results of an in vivo study'. A Moritz , U Schoop , K Goharkhay . *Journal of Clinical Laser Medicine and Surgery* 1998. 16 (4) p. .
- [Wefel ()] 'NovaMin: likely clinical success'. J S Wefel . *Adv Dent Res* 2009. 21 p. .
- [Litkowski ()] *Pilot clinical and in vitro studies evaluating NovaMin in desensitizing dentifrices Dent Res*, L Litkowski . 1998. 77 p. 199.

- 225 [Singh ()] 'Pro-Argin: a breakthrough technology for dentin hypersensitivity treatment'. S Singh . *Int J Sci Stu*
226 2013. 1 p. .
- 227 [Halappa ()] 'Pro-Argin: A Promising Technology for Dental Hypersensitivity'. Mythri Halappa . *Indian Journal*
228 *of Multidisciplinary Dentistry* 2015. 5 p. 68.
- 229 [Aun et al. ()] 'Raio laser-Hipersensibilidade dentinária'. C A Aun , A Brugnera-Júnior , R G Villa . *Revista da*
230 *APCD* 1989. 43 (2) p. .
- 231 [Narhi et al. ()] 'Responses of pulpal nociceptors to tissue injury and inflammation'. M V Narhi , M Addy , G
232 Embery , W M Edgar . *Tooth wear and sensitivity: clinical advances in restorative dentistry*, (London) 2000.
233 Martin Dunitz. p. .
- 234 [Yoshiyama et al. ()] 'Scanning electron microscopic characterization of sensitive vs. insensitive human radicular
235 dentin'. M Yoshiyama , J Masada , A Uchida , H Ishida . *J Dent Res* 1989. 68 p. .
- 236 [Brannstrom ()] *Sensitivity of dentin Oral Surgery Oral Medicine Oral Pathology*, M Brannstrom . 1966. 21 p. .
- 237 [Moritz et al. ()] 'Short-term assessment of the Nd: YAG laser with and without sodium fluoride varnish in
238 the treatment of dentin hypersensitivity-a clinical and scanning electron microscopy study'. A Moritz , U
239 Schoop , K Goharkhay . *Journal of Clinical Laser Medicine and Surgery* 1998 27. 2005. 16 (4) p. . (Journal
240 of Periodontology)
- 241 [Kumar and Mehta ()] 'Short-term assessment of the Nd: YAG laser with and without sodium fluoride varnish
242 in the treatment of dentin hypersensitivity-A clinical and scanning electron microscopy study'. N G Kumar ,
243 D S Mehta . *Journal of Periodontology* 2005. 76 (7) p. .
- 244 [Orchardson et al. ()] 'Strategies for the management of dentine hypersensitivity'. R Orchardson , M Addy , G
245 Embery , W M Edgar . *Tooth wear and sensitivity: clinical advances in restorative dentistry*, (London: Martin
246 Dunitz) 2000. p. .
- 247 [Ikemura ()] 'Studies on new treatment agents for dentin hypersensitivity'. R Ikemura . *Japanese Journal of*
248 *Conservative Dentistry* 1993. 36 p. .
- 249 [Matsumoto et al. ()] 'Study on the treatment of hypersensitive dentine by laser'. K Matsumoto , H Tomonari ,
250 H Wakabayashi . *Journal of Conservative Dentistry* 1985. 28 p. .
- 251 [Moritz et al. ()] 'The advantage of CO2-treated dental necks, in comparison with a standard method: results
252 of an in vivo study'. A Moritz , N Gutknecht , U Schoop . *Journal of Clinical Laser Medicine and Surgery*
253 1996. 14 (1) p. .
- 254 [Lan et al. ()] 'The combined occluding effect of sodium fluoride varnish and Nd: YAG laser irradiation on
255 human dentinal tubules'. W H Lan , H C Liu , C P Lin . *Journal of Endodontics* 1999. 25 (6) p. .
- 256 [Ling and Gillam ()] 'The effectiveness of desensitizing agents for the treatment of cervical dentin sensitivity
257 (CDS)-A review Journal of the Western Society of Periodontology'. T Y Ling , D G Gillam . *Periodontal*
258 *Abstracts* 1996. 44 (1) p. .
- 259 [Gillam et al. ()] 'The effects of oxalatecontaining products on the exposed dentine surface: an SEM investiga-
260 tion'. D G Gillam , N J Mordan , A D Sinodinou , J Y Tang , J C Knowles , I R Gibson . *J Oral Rehabil*
261 2001. 28 p. .
- 262 [Gaffar ()] *Treating hypersensitivity with fluoride varnish Compendium of Continuing Education in Dentistry*, A
263 Gaffar . 1999. 20 p. . (Supplement 1)